



2-27-2003

Microscopic Theory of Network Glasses

Randall W. Hall

Department of Chemistry, Louisiana State University, Baton Rouge, randall.hall@dominican.edu

Peter G. Wolynes

Department of Chemistry, Louisiana State University, Baton Rouge

Follow this and additional works at: <http://scholar.dominican.edu/all-faculty>

 Part of the [Chemistry Commons](#), and the [Physics Commons](#)

Recommended Citation

Hall, Randall W. and Wolynes, Peter G., "Microscopic Theory of Network Glasses" (2003). *Collected Faculty and Staff Scholarship*. 23.
<http://scholar.dominican.edu/all-faculty/23>

DOI

<http://dx.doi.org/10.1103/PhysRevLett.90.085505>

This Article is brought to you for free and open access by the Faculty and Staff Scholarship at Dominican Scholar. It has been accepted for inclusion in Collected Faculty and Staff Scholarship by an authorized administrator of Dominican Scholar. For more information, please contact michael.pujals@dominican.edu.

Microscopic theory of network glasses

Randall W. Hall

Department of Chemistry

Louisiana State University

Baton Rouge, La. 70803-1804

Peter G. Wolynes

Department of Chemistry and Biochemistry

University of California, San Diego

La Jolla, Ca. 92093-0332

(Dated: May 17, 2011)

Abstract

A molecular theory of the glass transition of network forming liquids is developed using a combination of self-consistent phonon and liquid state approaches. Both the dynamical transition and the entropy crisis characteristic of random first order transitions are mapped out as a function of the degree of bonding and the density. Using a scaling relation for a soft-core model to crudely translate the densities into temperatures, the theory predicts that the ratio of the dynamical transition temperature to the laboratory transition temperature rises as the degree of bonding increases, while the Kauzmann temperature falls relative to the laboratory transition. These results indicate why highly coordinated liquids should be "strong" while van der Waals liquids without coordination are "fragile".

PACS numbers: 61.43.Fs,64.70.Pf,65.60.+a

While much of the phenomenology of the glass transition is universal, shared by all dense liquids, everyday glasses are formed from liquids that possess a network structure at the molecular level. The universal features of the liquid-glass transition such as the Kauzmann entropy crisis and the Vogel-Fulcher rate law have been explained using theories based on an underlying random first-order transition[1, 2, 3], like that of mean field models with one step replica symmetry breaking[4]. Furthermore, the variations of the mean relaxation time[3] and degree of nonexponentiality[5] of relaxation from substance to substance have been quantitatively predicted using this approach, provided the configurational heat capacity is known as input, thus quantitatively explaining the patterns of behavior verbally characterized using the expression "liquid fragility"[6]. Detailed microscopic calculations buttressing these developments are based on a model of a dense interacting atomic fluid in which the particles interact via van der Waals forces alone. Is this starting point appropriate for the network glasses? To address this issue, we explore the glass transition in a model of a network forming liquid. The calculations presented are similar in spirit to those made earlier for atomic fluids. Our model assumes cross-linking in a liquid is fluctuating, not quenched as in models of rubber[7], taking the mean degree of crosslinking as given from experiment or from a separate calculation explicitly accounting for the equilibria between the various different bonded species. These calculations suggest a connection between the glassy behavior of network systems as viewed by random first order transition theory and rigidity percolation. Rigidity percolation features prominently in Phillips's discussion of the role of bonding constraints in glass formation[8], as well as in the extensive studies of Thorpe[9, 10]. A major result of the present calculations is that the density of non-bonded interactions needed to trigger energy landscape dominated glassy behavior decreases when bonding increases. It follows that, consistent with experiment, highly cross-linked network glasses should show

activated dynamics even at very high temperatures. The theory still predicts a crossover to non-activated dynamics for sufficiently high temperature as has recently been inferred in computer simulations of silica[11, 12].

The self-consistent phonon method applied to the amorphous state provides our starting point[13, 14]. This scheme is closely connected to approaches based on density functionals[15]. It has recently been justified by an elegant clone or replica approach[16, 17]. We actually use a hybrid of both density functional and self-consistent phonon calculations. For the hard sphere system, both approaches agree there is a critical density ρ_A , below which localized density distributions corresponding to amorphous packings are mechanically unstable to even small thermal fluctuations. $\rho_A\sigma^3$ from the self-consistent theory is approximately 1.0 for hard spheres, where σ is the hard sphere diameter. This is in agreement with the computer simulated dynamical transition[18]. This instability, from the vitrified side, coincides with the transition found in dynamical mode coupling approaches which start from the liquid side[1, 2, 19, 20]. The thermal vibration allowed at ρ_A in a frozen amorphous state gives mean square fluctuations $\langle \delta r^2 \rangle = \alpha^{-1}$, where α is an effective spring constant and is finite at the transition. α provides an analog of the Edwards-Anderson order parameter for spins and exhibits discontinuous replica symmetry breaking. This limit of stability for an amorphous system is comparable to the Lindemann criterion that describes melting of crystalline solids. At densities above ρ_A many different mechanically stable amorphous packings or free energy minima can exist. At densities beyond ρ_A , however, the configurational entropy of these minima decreases until it vanishes at a density ρ_K . Analogously, for soft-sphere models at fixed densities one can find a temperature T_A , signaling the onset of glassy dynamics (“landscape determined”[21]) and a still lower temperature T_K , the Kauzmann temperature where the configurational entropy would vanish. Between these

densities or temperatures, the dynamics can be described using the concept of entropic droplets[1, 2, 3, 5]. The activation free energy diverges as T_K is approached, consistent with the Vogel-Fulcher law $\Delta F^\ddagger = DT_K/(T - T_K)$. A microscopic calculation of the energy cost of forming an entropic droplet quantitatively explains the experimentally observed variation of D with the heat capacity drop upon vitrification, ΔC_p [3]. This correlation relies on the idea that the Lindemann ratio near T_K should depend only weakly on the detailed force law. We will check this supposition for our network glass model.

The free energy is computed for a given amorphous packing as a function of α . This free energy should then be averaged over packings. Each atom can be assigned to a cell and the density can be written as $\rho(\mathbf{r}) = \sum_i \rho_i = \sum_i \left(\frac{\alpha_i}{\pi}\right)^{3/2} \exp[-\alpha_i(\mathbf{r} - \mathbf{R}_i)^2]$ where the locations $\{\mathbf{R}_i\}$, characterize the packing as a set of fiducial locations around which the atoms vibrate. The free energy as a function of $\{\alpha_i\}$, $F(\{\alpha_i\})$, is analogous to the inter replica potential given as a function of q for spin glasses[22].

More generally, the thermal vibrations are described by a tensor α_i defined by

$$\alpha_i^{-1} = \langle (\mathbf{r}_i - \mathbf{R}_i)(\mathbf{r}_i - \mathbf{R}_i) \rangle_{W_i^{eff}} \quad (1)$$

where the averaging is with respect to the effective potential (dependent on $\{\alpha_j\}$)

$$\exp(-\beta W_i^{eff}) \equiv \prod_{i \neq j} \exp(-\beta V^{eff}(|\mathbf{r}_i - \mathbf{R}_j|)) = \prod_{i \neq j} \int d\mathbf{r}_j \rho_j(\mathbf{r}_j) \exp\left(-\frac{\beta}{2} V(r_{ij})\right) \quad (2)$$

where $V(r)$ is the potential energy. For an isotropic glass under the assumption that all α_i are the same V^{eff} becomes essentially a function of a scalar distance R , $V^{eff}(R)$, and one finds[14] $\alpha = \frac{\rho}{6} \int dR g(R) \nabla^2 (\beta V^{eff}(R))$ and a free energy $\frac{F(\alpha)}{Nk_B T} = f^{ideal} +$

$\rho \int dR g(R) V^{eff}(R)$. Although a good approximation for large α , the self-consistent phonon theory is not accurate for low α . At low α , an expansion around the uniform fluid can be used, but this depends on knowing the direct correlation function which is not available for network fluids. When no bonds are present, alternatively one can use the functional first suggested by Tarazona[23] and generalized by Ashcroft[24]. This functional takes the form $\frac{F}{Nk_bT} \equiv f = \frac{1}{N} \int dr \rho(r) [\log(\rho(r)) - 1] + \Psi(\eta)$ where Ψ is the interaction part of the free energy for a monatomic liquid or glass (which we take to be the Carnahan-Starling expression) and η is the packing fraction ($\pi\rho\sigma^3/6$). For the network forming liquids we will correct this free energy using a modification of the result of Erukhimovich[25], which provides for the entropy loss of forming bonds.

For the network forming liquid and glass, we separate the Hamiltonian into bonding and non-bonding parts $V = \sum_{i,j \text{ bonded}} V_b(r_{ij}) + \sum_{i,j \text{ non-bonded}} V_{nb}(r_{ij})$. Each pair i and j is considered to be either bonded or non-bonded and thus have an interaction described by either V_b or V_{nb} . The molecular units which are considered to be bonded have a locally harmonic potential energy $V_b(r_{ij}) = V_0 + \frac{1}{2}\gamma^b(r_{ij} - d_b)^2$ with d_b the equilibrium bond distance. V_{nb} , on the other hand, represents non-bonded interactions and therefore is taken to be a hard or soft sphere. Notice this potential does not explicitly describe, for any given configuration, whether a specific given pair should be considered bonded or not. This requires writing the potential using manybody switching functions[26, 27]. These manybody functions would reflect the saturation of chemical bonding tendencies (and would be needed for simulations.) For such a model the theory of associated liquids yields a (renormalized) equilibrium constant for the bonding reactions in terms of the underlying potential[28]. We will take the fraction of bonded pairs to be given and to be temperature and density independent. Of course, density and temperature dependent changes of the association equilibrium would be easy

to include, but would distract from understanding how the glassy physics itself depends on temperature. Provided the association equilibrium constants are not paradoxically related to the density (i.e., decrease partially with ρ) the trends in any event will be as shown.

For the network system, the self-consistent phonon calculation must distinguish the two types of interactions. For specificity we assume any given atom can form 0-4 bonds, in a tetrahedral pattern. Other spatial patterns are easily treated as well. At large α the effective potential coming from a bonded pair is essentially $V_b^{eff}(\mathbf{R}) = \frac{V_0}{2} + \frac{\gamma^b}{4} (|\mathbf{R}| - d_b)^2$ where the factor of 1/2 comes from the self-consistent formulation. We set the bond distance d_b equal to the hard sphere diameter for the non-bonded atoms and choose a zero of energy such that $V_0 = 0$. In numerical calculations we used $\beta\gamma^b = 300$, approximately the value appropriate for silica potentials[29]. The probability that a given atom has n -bonds, p_n is given by Erukhimovich[25] $p_n = \binom{4}{n} \Gamma^n (1 - \Gamma)^{4-n}$ with $\Gamma = \frac{n_b}{4}$ and n_b is the average number of bonds per atom.

In our calculations the basic pair distribution for non-bonded interactions, $g(R)$ is taken to be the Percus-Yevick radial distribution function modified for high density in the standard way. To account for the presence of bonded interactions that block the approach of other partners, $g(R)$ for an atom with n bonds (denoted $g_n(R)$) is scaled by $\max\left(0, \frac{\langle nn \rangle_\rho - n}{\langle nn \rangle_\rho}\right)$ for distances less than the first minimum of $g(R)$. $\langle nn \rangle_\rho$ is the number of nearest neighbors at total density ρ , obtained by integrating the first peak of $g(R)$.

To each of the 5 types of atoms, those with 0, 1, 2, 3, or 4 bonds, we assign a mean α_n . In this paper we use the *uncoupled oscillator* implementation of the self-consistent phonon theory[14] to determine the free energy. Essentially, this approximation treats the glass as a collection of Einstein oscillators. The derivation in Stoessel and Wolynes's early paper is lengthy in detail but when applied to the present potential one obtains

$$\begin{aligned}
F_{scp}/Nk_B T = & \sum_{n=0}^4 p_n \left[V_{b,n}^{eff}(d_b) + \rho \int dR g_n(R) V_{nb}^{eff}(R) \right] \\
& - \ln \int_v dr^N e^{-\sum_{n=0}^4 \frac{p_n}{2} r_i \cdot [\nabla \nabla \beta V_{b,n}^{eff}(R_i) + \mathbf{I} \alpha_n^{nb}] \cdot r_i} \quad (3)
\end{aligned}$$

where $V_{b,n}^{eff}$ is the sum of V_b^{eff} for an atom with n bonds over its bonds (and includes correlations between bonds through the use of a tetrahedral lattice), V_{nb}^{eff} is defined by Eqn. 2 using only the non-bonding potential energy and g_n , and α_n^{nb} is the non-bonding contribution to α_n . With a proper choice of local axes for each r_i , the argument of the exponential can be diagonalized, leading to 3 principal values of the vibrational tensor $\alpha_{1,n}$, $\alpha_{2,n}$, and $\alpha_{3,n}$. For the free energy to be consistent with Eqn. 1, we must have α_n satisfy $3\alpha_n^{-1} = \alpha_{1,n}^{-1} + \alpha_{2,n}^{-1} + \alpha_{3,n}^{-1}$. Note that for a glass transition to occur, all 3 components of α_n must be large. Given a bonding pattern, the $\{\alpha\}$ can be determined and, hence, the free energy.

F_{scp} is the free energy of the large α glassy minimum. We compute the free energy of the network liquid with $\alpha = 0$ using the Carnahan-Starling expression for a non-bonded liquid plus a modification of Erukhimovich's result for equilibrium network materials[25]: $F_{liq}/Nk_B T = \Psi(\eta) + 4 [\Gamma \ln \Gamma + (1 - \Gamma) \ln(1 - \Gamma)] + \ln\left(\frac{\rho}{e}\right) - \frac{n_b}{2} \ln\left(\frac{n_b \rho}{e}\right) + \frac{F_{scp}^b}{Nk_B T}$ where F_{scp}^b is obtained from Eqn. 3 with $\alpha = 0$ and only the bonding terms. It corresponds to the entropy loss from bonding computed by Erukhimovich[25].

The self-consistent phonon theory alone allows us to find ρ_A , as the lowest density giving a non-zero α , which thus corresponds to the onset of activated behavior while ρ_K , the "Kauzmann" density at which the free energies of the liquid and glass match and the configurational entropy vanishes also relies on the bonding correction to $F(\alpha = 0)$. The ratio

ρ_A/ρ_K dimensionlessly characterizes the thermodynamic aspects completely. To compare to the kinetic laboratory glass transition, we note the laboratory glass transition defined to occur when the viscosity reaches 10^{14} p. Previous work using random first order theory predicts this to occur when the configurational entropy is about $1.0 k_B$. To make the translation of our thermodynamic results to the laboratory transition density in what follows we will therefore mean by ρ_G the density where the liquid and glass free energies differ by $1.0 k_B T$ per particle. The universality of configurational entropy at the laboratory transition is well confirmed, also by experiment.

ρ_A , ρ_K , and ρ_G as functions of the average number of bonds n_b are shown in Fig. 1. For $n_b > 3$, ρ_A vanishes, indicating that the rigidity percolation occurs when $n_b = 3$ in our model. For comparison, Thorpe more precisely defining rigidity percolation as the absence of zero mode vibrational frequencies, finds $n_b = 2.4$. For $n_b > 3$, even at low densities the network is a rubber that can still vitrify at a higher densities. Fig. 2 shows the effective spring constants at these densities. For the hard sphere model[14] the uncoupled oscillator approximation leads to a somewhat lower ρ_A than simulation and to relatively small, but nevertheless finite, values of α_A . Quantitatively, the more complete coupled oscillator approximation (which uses a chain summation to treat the glass as a collection of Debye oscillators[14]) leads to a larger ρ_A in better agreement with computer studies. So we would expect quantitative modification by taking better account of the coupling but expect the same trend, namely that as the amount of bonding is increased, the transition densities decrease and therefore the transition temperatures increase. This theory then explains why the addition of a non-bonding impurity into a networked glass will lower the glass transition temperature, as known since ancient times for silica[30]. In physical terms, the non-bonding transition densities decrease because, as seen in Eqn. 3, as the contribution

from bonding to the vibrational force increases, the remaining contribution needed from non-bonding interactions for self-consistency decreases.

It is clear that ρ_A has a much sharper dependence on density than either ρ_K or ρ_G . The degree of bonding has a very direct effect on the vibrational force constant, being proportional to the average Laplacian of the effective potential, but only an indirect effect on entropy, entering through the more slowly varying (in space) Boltzmann factor. The theory explains the change of fragility with bonding. To see this we note that real liquids have both repulsive cores of finite strength and attractions which conspire in setting the equation of state. Yet assuming the attractions provide merely a smooth background potential the density dependences of this model can be translated into temperature dependences. For a soft potential $V \sim r^{-n}$ we have the scaling relation $T_1/T_2 = (\rho_2/\rho_1)^{3/n}$. Using this relation for $n = 12$ yields T_A/T_G and T_K/T_G as plotted in Fig. 3. Experimental measurements of T_K/T_G give 0.82 for the fragile glass orthoterphenyl[31], while for the strong glass silica the ratio has recently been determined[32] to be 0.36. The uncoupled oscillator approximation results in a variation from 0.82 for the non-networked glass to 0.6 at the approximate rigidity percolation limit, a variation somewhat smaller in magnitude. Doubtless, the crudeness of this result is due to our use of a scaling approximation appropriate to a simple, purely repulsive model and better agreement with experiment would be obtained by including attractive forces in our estimates. We see that T_A/T_G increases dramatically with n_b , while T_K/T_G decreases modestly. Thus highly bonded liquids have large temperature ranges of nearly Arrhenius activated behavior while liquids with few crosslinks have smaller ranges of strongly non-Arrhenius activated behavior.

For the uncoupled oscillator treatment α_A falls rapidly with density to very small values as crosslinking increases. The universality of the Lindemann ratio previously assumed by

Wolynes and coworkers[3] would seem in doubt. Yet this is not so. First, we know the coupled oscillator approximation will give a larger ρ_A therefore decreasing the range of variation of α_A . For $n_b = 0$, the coupled oscillator gives a value of $\alpha_A \approx 100$, while the uncoupled theory gives $\alpha_A \approx 20$ [14]. More important, even at the uncoupled level α_K and α_G are roughly constant with increasing bonding. A careful examination of the earlier analysis shows that these are the appropriate Lindemann-like ratios to determine the activation barriers in the strongly glassy regime. The predicted universal relation between D and ΔC_p , relying on a universal α_G , remains therefore sound.

The combination of self-consistent phonon and liquid state approaches provides a microscopic picture of network glasses that explains the dependence of the characteristic glass densities and, less directly, temperatures on degree of crosslinking and this results agrees with experiment. Doubtless, many of the detailed liquid state approximations made here can be improved but it is unlikely such modifications will change the qualitative story. In particular, the attractive forces that go beyond the soft-sphere model should probably be included to achieve quantitative agreement with experiment. This model combined with a theory of the association equilibria in forming the network provides a first principles treatment of glass properties starting from the underlying intermolecular forces.

RWH acknowledges NSF Grant. No. 9977124 for support.

[1] P.G.Wolynes, Acc. Chem. Res. **25**, 513 (1992).

[2] T.R.Kirkpatrick and D.Thirumalai, Transp. Theor. Stat.Phys. **24**, 927 (1995).

[3] X. Xia and P.G.Wolynes, PNAS **97**, 2990 (2000).

[4] D.J.Gross, I.Kanter, and H.Sompolinsky, Phys. Rev. Lett. **55**, 304 (1985).

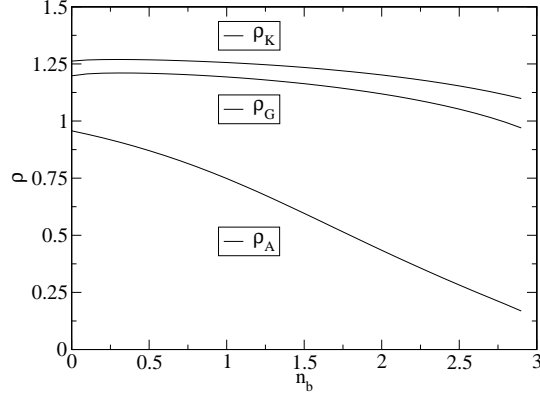


FIG. 1: Plot of ρ_A , ρ_K , and ρ_G versus n_b .

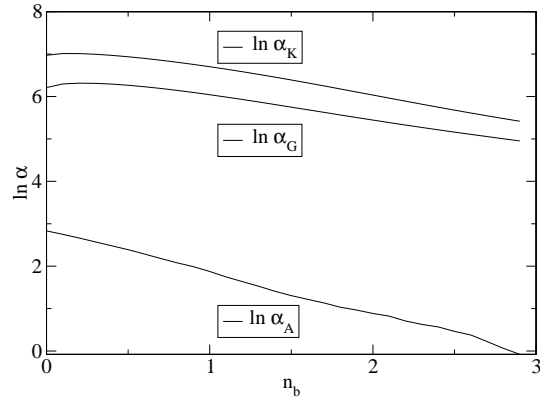


FIG. 2: Plot of $\ln \alpha_A$, $\ln \alpha_K$, and $\ln \alpha_G$ versus n_b .

[5] X. Xia and P.G.Wolynes, Phys. Rev. Lett. **86**, 5526 (2001).

[6] C.A.Angell, J. Non-Crystalline solids **73**, 1 (1985).

[7] P. Goldbart and N. Goldenfeld, Phys. Rev. A **39**, 1402 (1989).

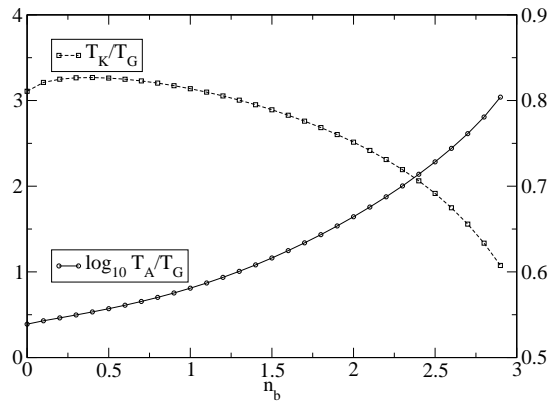


FIG. 3: Plot of $\log_{10}(T_A/T_G)$ (scale shown on left axis) and T_K/T_G (scale shown on right axis) versus n_b .

- [8] J.C.Phillips, Solid State Commun. **53** (1985).
- [9] S.Feng and M.F.Thorpe, Phys. Rev. B **31**, 276 (1985).
- [10] P.M.Duxbury, D.J.Jacobs, and M.F.Thorpe, Phys. Rev. E **59**, 2084 (1999).
- [11] J. Horbach and W. Kob, Phys. Rev. E **64**, 041503 (2001).
- [12] B. Coluzzi and P. Verrocchio, J. Chem. Phys. **116**, 3789 (2002).
- [13] M. Fixman, J. Chem. Phys. **51**, 3270 (1969).
- [14] J.P.Stoessel and P.G.Wolynes, J. Chem. Phys. **80**, 4502 (1984).
- [15] Y.Singh, J.P.Stoessel, and P.G.Wolynes, Phys. Rev. Lett. **54**, 1059 (1985).
- [16] S. Franz, M. Mezard, G. Parisi, and L. Peliti, J. Stat. Phys. **97**, 459 (1999).
- [17] M. Mezard and G. Parisi, **82**, 747 (1999).
- [18] L. Woodcock and C. Angell, Phys. Rev. Lett. **47**, 1129 (1981).
- [19] W. Götze, Condens. Matter **16**, 873 (1999).
- [20] U. Bengtzilius, W. Götze, and A. Sjölander, J. Phys. C **17**, 5915 (1984).
- [21] S.Sastry, P.G.Debenedetti, and F.H.Stillinger, Nature **393**, 554 (1998).
- [22] S.Franz and G.Parusi, Phys. Rev. Lett. **79**, 2486 (1997).
- [23] P.Tarazona, Molecular Physics **52**, 81 (1984).
- [24] A.Khein and N.W.Ashcroft, Phys. Rev. E **60**, 2875 (1999).
- [25] I. Erukhimovich, M. Thamm, and A. Ermoshkin, Macromolecules **34**, 5653 (2001).
- [26] F.H.Stillinger and T.A.Weber, Phys. Rev. B **31**, 5262 (1985).
- [27] L.R.Corrales and P.J.Rosky, Chem. Phys. Lett. **194**, 363 (1992).
- [28] L.W.Dahl and H.C.Andersen, J. Chem. Phys. **78**, 1962 (1983).
- [29] B. van Beest, G. Kramer, and R. van Santen, Phys. Rev. Lett. **64**, 1955 (1990).
- [30] Pliny the Elder, *Natural History* (xxxvi, 65).

[31] C. Angell, J. Res. NIST **102**, 171 (1997).

[32] A. Sipp, Y. Bottinga, and P. Richet, J. Non-Crystalline solids **288**, 166 (2001).